



## Metallic-Coated Products and Specifications

Rev 2.2 Apr 2014

### Understanding Coating Weight Designations for Zinc-Based Coatings on Steel Sheet

#### Introduction

One of the most confusing aspects of coated steel sheet products are coating weight designations and what they mean, particularly with respect to product performance. This article is intended to clarify this issue.

#### Coating Weight [Mass] Designation Systems

Each coated steel sheet product has its own coating weight designation system, which is defined in the appropriate ASTM standard. For example, the most widely used ASTM metallic-coated sheet standard is A653/A653M, which covers hot-dip galvanized products. One of the coating weight designation systems in this standard uses descriptors such as G60, G90, etc. The “G” means the coating is galvanize (zinc), and the numbers refer to the weight of zinc on the surface of the steel sheet in inch-pound (English/Imperial) units. Taking G90 as an example, the coating weight on one square foot of sheet (total-both-sides of the sheet) shall have a triple spot test (TST) average minimum of 0.90 ounces. If equally applied to both sides of the sheet, there would be a minimum of 0.45 ounces on each square foot of surface.

The other measurement system in widespread use today is the SI [Metric] system. The conversion from the inch-pound weight<sup>1</sup> in ounces per square foot (oz/ft<sup>2</sup>) to the SI mass<sup>2, 3</sup> in grams per square metre (g/m<sup>2</sup>) is:

$$1.00 \text{ oz/ft}^2 = 305 \text{ g/m}^2$$

To convert from oz/ft<sup>2</sup> to g/m<sup>2</sup>, multiply by 305

Example: G90 (0.90 oz/ft<sup>2</sup>) = Z275 (275 g/m<sup>2</sup>)

If what we are interested in is the coating thickness, why do ASTM standards not use thickness measurements? The answer is simply that it is difficult to directly measure the thickness accurately. For example, a G90 coating contributes about 1.6 mils (0.0016 inches, or about 42 microns) to the total thickness of the coated sheet. For a coating equally applied to both sides of the sheet, this means there is about 0.0008 inches (21 microns) of zinc on each surface. To accurately determine the thickness of the coating, the coated thickness must be measured, the coating stripped off, and then the steel substrate thickness measured using a gauge capable of accurately reading to the nearest ten-thousandth of an inch. This is extremely difficult to do with good accuracy. On-line equipment is available that can nondestructively do this (see sidebar), but the most accurate manual method of determining the amount of coating present is to measure its weight [mass] on a given surface area using the “weigh-strip-weigh” technique. Weigh-strip-weigh refers to the procedure of weighing a standard size sample of the product

#### COATING WEIGHT MEASUREMENT

*There is a very precise on-line technique for measuring coating thickness. The equipment required is expensive, uses sophisticated x-ray or radioisotope fluorescence devices, and requires considerable expertise to operate. These gauges repeatedly sense the coating thickness on each surface, average a large number of readings, and then convert the results to the more familiar coating weight units. Laboratory versions of this equipment are also available. Refer to ASTM Test Method A754 for more information. These gauges require calibration based on weigh-strip-weigh testing.*

<sup>1</sup> Weight is a measure of the pull of the force of gravity (Weight/Force = Mass x Acceleration of gravity)

<sup>2</sup> Mass is a fundamental property – the same everywhere

<sup>3</sup> For the purpose of measuring metallic coatings, mass and weight are equivalent everywhere on earth

using a very accurate scale, stripping the coating in an inhibited acid without removing any of the substrate, then reweighing the coupon to determine the weight [mass] loss. This is the original method of determining coating weight [mass], and, in fact, is still the referee method used to check and calibrate nondestructive on-line and laboratory coating thickness gauges. There are weigh-strip-weigh procedures that can be used for all zinc-based coatings in commercial production today. For the most common products, these procedures are defined in ASTM Standard A90/A90M, and cover galvanized and galvanized sheet, 55% aluminum-zinc alloy-coated sheet, zinc-5% aluminum alloy-coated sheet, and zinc-aluminum-magnesium alloy-coated sheet. There are special procedures required for other types of alloy coatings such as aluminized, and zinc-nickel alloy electroplated sheet. These are covered by other ASTM standards.

## ASTM Coating Designations – What do they specify?

- ASTM designations for hot-dip coated sheet specify:
  - Minimum triple spot test (TST) value
    - Average of three edge-center-edge readings
    - **A total-both-sides (TBS) requirement** (See A924/A924M for testing details)
  - Minimum single spot test (SST) value
    - A single spot **TBS requirement**, and
  - Minimum single side requirement
    - **Is based on a TST only!**
- The TST test **only applies to the original, full-width (as-coated) sheet**
- Narrow sheet cut from full-width sheet is subject only to a minimum SST, TBS requirement
- With the exception of supplementary Table S2.1 in A653/A653M, ASTM specifications **are silent** on the minimum weight on one side of a single spot
- Examples of full-width pass/fail test results for A653 are given below

**Table 1 Example G90 Coating Weight Results - Illustrating Passing and Failing the Requirements of A653/A653M (Table 1) – values in oz/ft<sup>2</sup>**

Requirements of A653 (Table 1):

Minimum Triple Spot Test average (TST), Total Both Sides (TBS) – 0.90 oz/ft<sup>2</sup>

Minimum Single Spot Test (SST), Total Both Sides (TBS) – 0.80 oz/ft<sup>2</sup>

Minimum One Side (OS), Triple Spot Test average (TST) – 0.32 oz/ft<sup>2</sup> (per Footnote A of A653 Table 1)

Example	Test	E1	E2	E3	TST	Comments
1	TBS	0.92	0.93	0.96	<b>0.94</b>	<b>Passes</b> min TST
2	TBS	0.85	0.93	0.96	<b>0.91</b>	<b>Passes</b> min TST
3	TBS	0.85	0.87	0.96	<b>0.89</b>	<b>Fails</b> on min TST
4	TBS	<b>0.78</b>	0.95	0.96	0.90	<b>Fails</b> on min SST
5	OS-Top	<b>0.30<sup>1</sup></b>	<b>0.31<sup>1</sup></b>	0.40	<b>0.34</b>	<b>Passes</b> on min TST-OS & TBS
	OS-Bot	0.55	0.62	0.47	0.54	
	TBS	0.85	0.93	0.96	<b>0.91</b>	
6	OS-Top	0.30	0.31	0.31	<b>0.31</b>	<b>Fails</b> on min TST-OS
	OS-Bot	0.55	0.62	0.65	0.60	
	TBS	0.85	0.93	0.96	0.91	

<sup>1</sup> These values meet the specification, since the One Side, Triple Spot Test average is above 0.32 oz/ft<sup>2</sup>

## Designation System for Galvanized and Galvannealed Sheet Products

**Galvanize** – For galvanized sheet, common inch-pound coating weight designations (ordered as A653 or A1063) are, in oz/ft<sup>2</sup>:

G30            G40            G60            G90            G115

These designations specify the minimum average TST, total-both-sides, tested per ASTM A924/A924M, e.g., G90 requires a minimum average TST of 0.90 oz/ft<sup>2</sup> total-both-sides. The specification stipulates that TST samples shall be taken from defined positions at the edge-center-edge of the as-coated sheet.

There are designations for heavier coatings, such as G165 and G210, but these products are used for very specialized applications and are generally not available on thinner gauge sheet.

In SI units (ordered as A653M or A1063M), the comparable coating mass designations for galvanized sheet are, in g/m<sup>2</sup>:

Z90            Z120            Z180            Z275            Z350

These designations specify the minimum average TST, total-both-sides, tested per A924/A924M, e.g., Z275 requires a minimum average TST of 275 g/m<sup>2</sup> total-both-sides.

In 2007 ASTM added the option of ordering single side, single spot test (SST) coating designations to A653/A653M. These are SI designations only (ordered to A653M) and specify the minimum and maximum allowable coating mass per side for any SST. They take the familiar form of automotive coating designations (numeric characters first – signifying a per side requirement). No inch-pound designations are used since single side coatings are traditionally ordered in SI units only. Examples are:

60G            70G            90G

These designations specify the minimum and maximum SST value on each surface, e.g., 60G requires a minimum of 60 g/m<sup>2</sup> and a maximum of 110 g/m<sup>2</sup> of zinc on each surface for any SST.

When specifying single side single spot coatings, the designation for each surface must be shown, e.g., 60G60G.

**Zinc-Iron (Galvanneal)** – The common inch-pound coating weight designations (ordered as A653) for galvannealed sheet (zinc-iron alloy-coated) are, in oz/ft<sup>2</sup>:

A25            A40            A60

As with galvanized product designators, A40 for example, requires a minimum average TST coating weight of 0.40 oz/ft<sup>2</sup>, total-both-sides. While the coating contains approximately 8 to 10% iron, resulting in the density being slightly higher than a zinc coating and the coating thickness being slightly less than a G40 galvanize coating, the difference is too small to be of concern. The effect of density is discussed in the section on 55% Al-Zn coatings, and in GalvInfoNote 1.10. Also, see GalvInfoNote 1.3 for a full explanation of hot-dip galvanneal coatings.

The SI equivalent coating mass designations (ordered as A653M) for galvannealed sheet are, in g/m<sup>2</sup>:

ZF75            ZF120            ZF180

ZF120, for example, requires a minimum average TST of 120 g/m<sup>2</sup> total-both-sides.

**Coating weight [mass] versus coating life** – For galvanized coatings in most applications and environments, the corrosion performance is an approximate linear function of coating weight (thickness). For instance, a G60 coating has twice the thickness of a G30 coating, and the life of the product (defined, perhaps, as the time to 5% red rust) in a given environment is approximately twice as long. Similarly, a G90 coating is approximately 50% thicker than a G60 coating, and thus would be expected to perform 50% better (in terms of time to 5% red rust). For a more thorough discussion on service life, see GalvInfoNote 3.1. Limits on maximum acceptable coating weights for an application are usually determined by other factors such as cost or formability. For a more thorough discussion of this topic see GalvInfoNotes 1.6 and 2.5.

For other metallic-coated sheet products, the life versus coating thickness is typically not linear; thus determining the coating weight [mass] to use is not as simple as it is for galvanized coatings. Also, when these products are painted, the behaviour is even more complex. The subject of painted hot-dip products is addressed in GalvInfoNotes 4.1 and 4.2.

As with galvanize, the option of ordering zinc-iron coatings to single side, SST coating designations has been added to A653/A653M. Again, these are SI designations only (ordered to A653M), specifying the minimum and maximum allowable coating mass per side for any single spot, and taking the familiar form of automotive coating designations (numeric characters first – signifying a per side requirement). No inch-pound designations are used since single side coatings are traditionally ordered in SI units only. Examples are:

45A                      50A

These designations relate to the minimum and maximum SST value on each surface, e.g., 45A requires a minimum of 45 g/m<sup>2</sup> and a maximum of 75 g/m<sup>2</sup> of zinc-iron alloy on each surface for any SST.

When specifying single side, SST coatings, the designation for each surface must be shown, e.g., 45A45A.

.....

For galvanized and galvanized sheet, the three-significant figure relationship between coating weight [mass] and thickness (**based on zinc density of 446 lb/ft<sup>3</sup> [7140 kg/m<sup>3</sup>]**) is:

$$1.00 \text{ oz/ft}^2 = 0.00168 \text{ in} = 305 \text{ g/m}^2 = 0.0427 \text{ mm} \quad (1)$$

## Designation System for Electrogalvanized Sheet Products

For electroplated coatings (pure zinc and zinc-based alloy coatings), SI system (g/m<sup>2</sup>) designators are most commonly used, although ASTM Standard A879/A879M for electrogalvanize includes the inch-pound [oz/ft<sup>2</sup>] designator system. The reason for the initial use of SI designators is that many electroplated products were and still are used for automotive applications. Automobile producers, who implemented worldwide coated sheet specifications many years ago, use only SI units.

For electrogalvanized sheet, common inch-pound coating weight designations (ordered as A879) are, in oz/ft<sup>2</sup>:

08Z                      13Z                      30Z

These designations relate to the minimum and maximum SST value on each surface, as defined in ASTM A879/A879M, e.g., 13Z requires a minimum of 0.13 and a maximum of 0.23 oz/ft<sup>2</sup> of zinc on each surface for any SST. Again, the numeric characters come first, signifying per side requirements.

When specifying, the designation for each surface must be shown, e.g., 13Z13Z.

For electrogalvanized sheet, common SI coating weight designations (ordered as A879M) are, in g/m<sup>2</sup>:

24G                  40G                  90G

These designations relate to the minimum and maximum SST value on each surface, as defined in ASTM A879/A879M, e.g., 40G requires a minimum of 40 and a maximum of 90 g/m<sup>2</sup> of zinc on each surface for any SST.

Again, the designation for each surface must be shown, e.g., 40G40G.

See GalvInfoNote 2.2 for an explanation of the electrogalvanizing process.

## Keeping ASTM Designation Systems Straight

As hot-dip galvanized and galvanized coatings saw more use by the automotive industry, it became the practice to manufacture these products to conform to single side, SST g/m<sup>2</sup> values; that being the requirement of automotive manufacturers. Products ordered for construction and other general end uses continue to be ordered to total-both-sides, TST, inch-pound designations. For hot-dip galvanize, as we have seen, ASTM uses “G” (prior to the numerals) in the designator for inch-pound coatings and “Z” for SI coatings – total-both-sides in each case. On the other hand, for electrogalvanize “G” (after the numerals) means SI units and “Z” means inch-pound units – single spot, single side in each case.

The use of both dimensional units, and the reversal of “G” and “Z” between TST hot-dip, and single side, SST EG in ASTM specifications, certainly can lead to confusion in the marketplace. Table 2 below summarizes what the various designations mean in terms of single spot and triple spot requirements.

**Table 2 Galvanized Sheet Coating Designations Explained**

Coating Designation Format	Product Type and Coating Requirements						
	Specification	Coating	Units	Coating Tests Required			
				Single Side		Total Both Sides	
				SST	TST	SST	TST
<b>Gnn</b>	A653 – Table 1	Zinc - HD	oz/ft <sup>2</sup>	NONE	Min	Min	Min
<b>Znn</b>	A653M – Table 1	Zinc - HD	g/m <sup>2</sup>	NONE	Min	Min	Min
<b>Ann</b>	A653 – Table 1	Zinc-iron - HD	oz/ft <sup>2</sup>	NONE	Min	Min	Min
<b>ZFnn</b>	A653M – Table 1	Zinc-iron - HD	g/m <sup>2</sup>	NONE	Min	Min	Min
<b>nnZnnZ</b>	A879	Zinc - EG	oz/ft <sup>2</sup>	Min & Max	NONE	NONE	NONE
<b>nnGnnG</b>	A879M	Zinc - EG	g/m <sup>2</sup>	Min & Max	NONE	NONE	NONE
<b>nnGnnG</b>	A653 M – Table S2.1	Zinc - HD	g/m <sup>2</sup>	Min & Max	NONE	NONE	NONE
<b>nnAnnnA</b>	A653 M – Table S2.1	Zinc-iron - HD	g/m <sup>2</sup>	Min & Max	NONE	NONE	NONE
<b>nnGnnG</b>	Auto (typical) 1	Zinc - HD & EG	g/m <sup>2</sup>	Min & Max	NONE	NONE	NONE
<b>nnAnnnA</b>	Auto (typical) 2	Zinc-iron - HD & EG	g/m <sup>2</sup>	Min & Max	NONE *	NONE	NONE

Notes: nn = numerals (2 or 3) specific to coating weight [mass]

HD = Hot-Dip

EG = Electrogalvanize

SST = Single Spot Test

TST = Triple Spot Test

\* some auto manufacturers require a minimum TST

For additional clarification, see Table 3 below, which provides the requirements of selected coating weight [mass] examples for galvanized sheet made to ASTM specifications.

It is not easy to keep the terminology straight. Users should be aware that both units are in common use today, and are advised to pay close attention when ordering, knowing precisely what is meant by the terminology being used. See the Table 4 at the end of this article, which summarizes the designations used for most hot-dip products, and may be useful in keeping terminology clear.

**Table 3 Selected ASTM Galvanized Sheet Designations – Requirements**

Product Type	Example Designation	Requirement
Hot-Dip Galvanize (A653/A653M)	G90 (A653, Table 1, in-lb)	TST <sup>a</sup> average 0.90 oz/ft <sup>2</sup> min – total both sides TST average 0.32 oz/ft <sup>2</sup> min – each side SST <sup>b</sup> 0.80 oz/ft <sup>2</sup> min – total both sides
	Z275 (A653M, Table 1, SI)	TST average 275 g/m <sup>2</sup> min – total both sides TST average 94 g/m <sup>2</sup> min – each side SST 235 g/m <sup>2</sup> min – total both sides
	60G60G (A653M, Table S2.1, SI) <sup>c</sup>	SST 60 g/m <sup>2</sup> min, 110 g/m <sup>2</sup> max – each side
Hot-Dip Galvanneal (A653/A653M)	A40 (A653, Table 1, in-lb)	TST average 0.40 oz/ft <sup>2</sup> min – total both sides TST average 0.12 oz/ft <sup>2</sup> min – each side SST 0.30 oz/ft <sup>2</sup> min – total both sides
	ZF120 (A653M, Table 1, SI)	TST average 120 g/m <sup>2</sup> min – total both sides TST average 36 g/m <sup>2</sup> min – each side SST 90 g/m <sup>2</sup> min – total both sides
	45A45A (A 53M, Table S2.1, SI)	SST 45 g/m <sup>2</sup> min, 75 g/m <sup>2</sup> max – each side
Electrogalvanize (A879/A879M)	13Z13Z (A879, Table 1, in-lb)	SST 0.13 oz/ft <sup>2</sup> min, 0.23 oz/ft <sup>2</sup> max – each side
	40G40G (A879M, Table 1, SI)	SST 40 g/m <sup>2</sup> min, 70 g/m <sup>2</sup> max – each side

<sup>a</sup> – Triple Spot Test      <sup>b</sup> – Single Spot Test

<sup>c</sup> – For information purposes, Table S2.1 in A 653M shows inch-pound values for the SI coating designations


## Total Both Side TST versus Single Side SST Coatings

Because the ASTM total-both-sides, TST designators allow an uneven split of the coating (one side TST must have at least 40% of the specified minimum SST total-both-sides coating weight), it is not possible to precisely convert them to SST, single side designators since the latter specify exact minimums per surface. It is sometimes useful, however, to provide an approximate conversion based on the total coating thickness on both surfaces.

Figure 1 on the next page is a chart that allows this to be done, both in terms of coating designators and thickness of the total coating. For instance, it can easily be seen that a G60 coating has a minimum total-both-sides thickness of about 1.0 mil, which is the very close to twice the minimum per side thickness (2 x

12.5 microns) of a 90G90G coating. Remember, however, that a G60 coating is an average of 3 readings (TST) and can have an uneven split of the total coating thickness, while a 90G90G coating must have a minimum of 12.5 microns on each side for any single spot.

Figure 1 is a guideline only for estimating coating thickness in terms of the two systems and is not meant to suggest equivalency. Also, the values shown are specified minimums. Actual coatings are always a few percent thicker in order to guarantee the minimums.

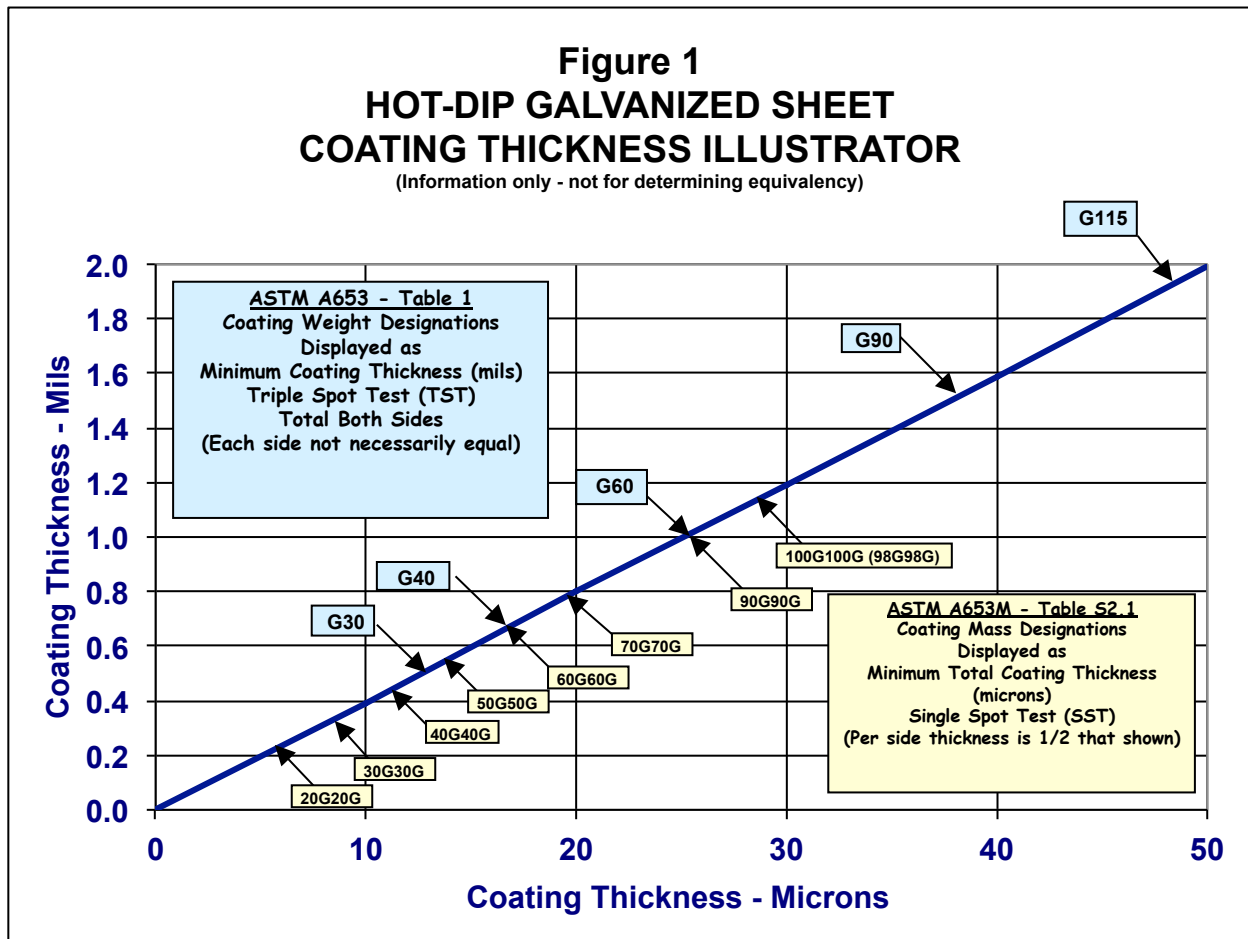

## Designation System for 55% Aluminum-Zinc Alloy-Coated Sheet

Steel sheet with a 55% aluminum-zinc alloy coating (55% Al-Zn alloy-coated) is in common use today throughout the construction and appliance industries. It, too, has very specific coating designators. Fortunately, there are only a few designators, but that doesn't mean there is no confusion about the meaning. The designation systems for coating weight and coating mass are given in ASTM Standard A792/A792M.

The four inch-pound coating weight designations (ordered as A792) are, in oz/ft<sup>2</sup>:

AZ50      AZ55      AZ60      AZ70

These designations specify the minimum average of a TST, total-both-sides, tested per A924/A924M, e.g., AZ50 requires a minimum average TST of 0.50 oz/ft<sup>2</sup> total-both-sides.



*These designators are comparable to those used for galvanized sheet in that the dimensions are oz/ft<sup>2</sup>. Be aware, however, that the designation AZ60 is not equivalent to a G60 coating with respect to the thickness of the coating. Here is where the issue of density comes into play. The coating on 55% Al-Zn alloy coated sheet has 55% aluminum and about 45% zinc. Actually, the coating has a small addition of silicon, but for purposes of this discussion the silicon is not important. Since aluminum is less dense than zinc (a given volume weighs less than the same volume of zinc), an AZ60 coating is thicker than a G60 galvanize coating. See the section on theoretical weight [mass] in GalvInfoNote 1.10 to understand how differences in coating density affect coated sheet.*

*Because 55% Al-Zn alloy coating and a galvanize coating behave quite differently with respect to corrosion processes, drawing a performance equivalency curve is not possible. There is no answer, therefore, to the question: What 55% Al-Zn alloy coating is equivalent in performance to a G90 coating? The major use of 55% Al-Zn alloy coated sheet is for construction industry building panels, and for this application the most common coating weights are AZ50 [AZM150] and AZ55 [AZM165]. As the differences in performance between these two designators are subtle, ask your supplier which coating thickness is recommended for your application.*

For 55% Al-Zn alloy-coated sheet there is also a SI coating mass designator system (ordered as A792M). The SI equivalents to AZ50, AZ55, AZ60 and AZ70 are, in g/m<sup>2</sup>:

AZM150      AZM165      AZM180      AZM210

These designations specify the minimum average of a TST, total-both-sides, per A924/A924M, e.g., AZM150 requires a minimum TST of 150 g/m<sup>2</sup> total-both-sides.

Since 55% Al-Zn alloy-coated sheet is produced only by the hot-dip process, there is no additional terminology or specification related to the manufacture of an electroplated product. Also, there are no SST, single side designations for this product.

For 55% Al-Zn alloy-coated sheet, the three-significant figure relationship between coating weight [mass] and thickness (**based on an alloy density of 234 lb/ft<sup>3</sup> [3750 kg/m<sup>3</sup>]**) is:

$$1.00 \text{ oz/ft}^2 = 0.00320 \text{ in} = 305 \text{ g/m}^2 = 0.0813 \text{ mm} \quad (2)$$

See GalvInfoNote 1.4 for a complete description of 55% Al-Zn alloy-coated sheet.

## Designation System for Zinc-5% Aluminum Alloy-Coated Sheet

Steel sheet with a zinc-5% aluminum alloy coating (Zn-5% Al alloy-coated) is used by the construction, automotive, and appliance industries. Zn-5% Al alloy-coated sheet has a coating that consists of 95% zinc and 5% aluminum, and small amounts of other elements to improve processing and product characteristics. The designation systems for coating weight and coating mass are given in ASTM Standard A875/A875M.

The common inch-pound coating weight designations (ordered as A875) are, in oz/ft<sup>2</sup>:

GF30      GF45      GF60      GF75      GF90

These designations specify the minimum average of a TST, total-both-sides, tested per A924/A924M, e.g., GF60 requires a minimum average TST of 0.60 oz/ft<sup>2</sup> total-both-sides.

For Zn-5% Al alloy-coated sheet, since the coating contains about 95% zinc, and thus has nearly the same density as zinc, a GF90 coating is approximately equivalent in thickness to a G90 galvanized coating.

The equivalent SI coating mass designations (ordered as A875M) are, in g/m<sup>2</sup>:

ZGF90      ZGF135      ZGF180      ZGF225      ZGF275



These designations specify the minimum average of a TST, total-both-sides, per A924/A924M, e.g., ZGF180 requires a minimum TST of 180 g/m<sup>2</sup> total-both-sides.

As with 55% Al-Zn alloy-coated sheet, Zn-5% Al alloy-coated sheet is made only by the hot-dip process so there are no designator systems that involve per side terminology.

For Zn-5% Al alloy-coated sheet, the three-significant figure relationship between coating weight [mass] and thickness (**based on an alloy density of 427 lb/ft<sup>3</sup> [6840 kg/m<sup>3</sup>]**) is:

$$1.00 \text{ oz/ft}^2 = 0.00175 \text{ in} = 305 \text{ g/m}^2 = 0.0446 \text{ mm} \quad (3)$$

See GalvInfoNote 1.9 for a complete description of Zn-5% Al alloy-coated sheet.

### Designation System for Zinc-Aluminum-Magnesium Alloy-Coated Sheet

A fourth type of zinc-based coating that is used where superior corrosion resistance is needed, is zinc-aluminum-magnesium alloy-coated (Zn-Al-Mg alloy-coated) sheet. This alloy-coated sheet has a coating that consists of zinc with 5-13% aluminum, and 2-4% magnesium. The designation systems for coating weight and coating mass are given in ASTM Standard A1046/A1046M.

The common inch-pound coating weight designations (ordered as A1046) are, in oz/ft<sup>2</sup>:

ZM30      ZM40      ZM60      ZM75      ZM90

These designations specify the minimum average of a TST, total-both-sides, tested per A924/A924M, e.g., ZM60 requires a minimum average TST of 0.60 oz/ft<sup>2</sup> total-both-sides.

The equivalent SI coating mass designations (ordered as A1046M) are, in g/m<sup>2</sup>:

ZMM90      ZMM120      ZMM180      ZMM220      ZMM275

These designations specify the minimum average of a TST, total-both-sides, per A924/A924M, e.g., ZMM180 requires a minimum TST of 180 g/m<sup>2</sup> total-both-sides.

As with 55% Al-Zn alloy-coated sheet, Zn-Al-Mg alloy-coated sheet is made only by the hot-dip process so there are no designator systems that involve per side terminology.

For Zn-Al-Mg alloy-coated sheet, the three-significant figure relationship between coating weight [mass] and thickness (**based on a density of 375 lb/ft<sup>3</sup> [6004 kg/m<sup>3</sup>] for 5-9% Al alloy; and 357 lb/ft<sup>3</sup> [5720 kg/m<sup>3</sup>] for 9-13% Al alloy**) is:

$$\text{For 5-9\% Aluminum: } 1.00 \text{ oz/ft}^2 = 0.00200 \text{ in} = 305 \text{ g/m}^2 = 0.0508 \text{ mm} \quad (4)$$

$$\text{For 9-13\% Aluminum: } 1.00 \text{ oz/ft}^2 = 0.00210 \text{ in} = 305 \text{ g/m}^2 = 0.0533 \text{ mm} \quad (5)$$

## Summary

This article explains the complexities of coating designation systems and hopefully provides a better understanding of why it is important to be sure that you and your supplier are speaking the same language. Table 4 gives examples of some of the designators discussed above. See GalvInfoNote 1.10 for an explanation of how coatings affect the metrics of coated steel sheet products.

**Table 4 Designators for Zinc-Based Coatings on Steel Sheet - SUMMARY**

Product	Example of Common Coating Designations		Coating Weight inch-pound oz/ft <sup>2</sup>	Coating Mass SI g/m <sup>2</sup>
	inch-pound	SI		
Total Both Sides - Minimum Triple Spot Average				
ASTM A653/A653M Galvanize	G90	Z275	0.90	275
ASTM A653/A653M Galvanneal	A40	ZF120	0.40	120
ASTM A792/A792M 55% Al-Zn alloy-coated	AZ55	AZM165	0.55	165
ASTM A875/A875M Zn-5% Al alloy-coated	GF75	ZGF225	0.75	225
ASTM A1046/A1046M Zn-Al-Mg alloy-coated	ZM90	ZMM275	0.90	275
Single Side <sup>++</sup> - Minimum Single Spot				
ASTM A653M Galvanize (Table S2.1)	N/A*	60G	0.20	60
ASTM A653M Galvanneal (Table S2.1)	N/A*	45A	0.15	45
ASTM A879/A879M Electrogalvanize	13Z	40G	0.13	40
Automotive Specified Galvanize	N/A*	100G	N/A*	100
Automotive Specified Galvanneal	N/A*	45A	N/A*	45

\* Not Applicable

<sup>++</sup> Single side designators are used to specify the coating mass for each side and are written, for example, 60G60G, or in the case of differential coating masses, 90G60G.

Copyright© 2014 – IZA

### Disclaimer:

Articles, research reports, and technical data are provided for information purposes only. Although the publishers endeavor to provide accurate, timely information, the International Zinc Association does not warrant the research results or information reported in this communication and disclaims all liability for damages arising from reliance on the research results or other information contained in this communication, including, but not limited to, incidental or consequential damages.

**Indian Steel Sheet Building Group**  
email: kdesouza@zinc.org

*This document has been repurposed from galvinform.com as part of the ISSBG program in India.*